

## The Ternary Systems: Cr-Al-C, V-Al-C, and Ti-Al-C and the Behavior of H-Phases ( $M_2AlC$ )

J. C. SCHUSTER, H. NOWOTNY,\* AND C. VACCARO

*Institute of Materials Science, The University of Connecticut, Storrs, Connecticut 06268*

Received March 20, 1979; in final form July 12, 1979

Phase relationships in the ternary systems Cr-Al-C, V-Al-C, and Ti-Al-C have been investigated. All previously reported ternary H-phase  $Me_2AlC$  ( $Me = Cr, V, Ti$ ) and the perovskite phase  $Ti_3AlC$  are confirmed. No new ternary phase was found. At 1000°C  $Ti_2AlC$  and  $Ti_3AlC$  are coexistent. In addition, the H-phase was found in equilibrium with  $TiC_{1-x}$ ,  $TiAl_3$ , and  $TiAl$ ; the perovskite with  $TiC_{1-x}$ ,  $Ti_3Al$ , and  $Ti$  (solid solution with Al).  $TiC_{1-x}$  coexists with Al(l) at temperatures above 800°C.  $V_2AlC$  coexists at 1000°C with  $Al_4C_3$ , Al(l),  $Al_3V$ ,  $V_7Al_8$ , V (solid solution with Al),  $V_2C$ ,  $\zeta$ - $VC_{1-x}$ , and  $VC_{1-x}$  (including  $V_8C_7$ ). At 1000°C  $Cr_2AlC$  is in equilibrium with  $Al_4C_3$ ,  $\gamma$ - $Cr_5Al_8$ , Cr (solid solution with Al),  $Cr_7C_3$ , and  $Cr_3C_2$ . At 800°C  $Cr_2AlC$  coexists also with graphite and  $\beta$ - $Cr_2Al$ .  $V_2AlC$  forms a complete series of solid solutions with  $Cr_2AlC$  and  $Ti_2AlC$ . At about 1000°C the solid solution series  $Ti_2AlC$ - $Cr_2AlC$  exhibits a miscibility gap.

### Introduction

Among so-called complex carbides (1) formed by two metals and carbon, the ternary combinations involving transition element ( $M$ )-B-group element (metametal) ( $M'$ )-carbon, carbides of formula  $M_3M'C$  (perovskite carbides) and  $M_2M'C$  (H-phase) display a surprisingly wide occurrence. This reflects somewhat the simple geometry of crystal structure in both these types of phases and the filling mode by an interstitial stabilizer (carbon). The filling mode can clearly be seen from the fact that other nonmetal stabilizers such as nitrogen (and oxygen) also form numerous perovskite or H-phases. Furthermore carbon deficiency, which is very typical for interstitial alloys, has been found for perovskite carbides, but stoichiometric compositions or appreciable

homogeneous domains have also been detected in H-phases, for example,  $Nb_2SC_{1-x}$  ( $x = 0-0.6$ ), where sulfur replaces the metametal.

It is noteworthy that the structural array of the perovskite-type carbide represents an antitype of the nonmetallic perovskite ( $CaTiO_3$ ). The correspondence of metallic structure types and nonmetallic (saltlike) structure types or vice versa has been widely observed (2) and quite recently the crystal structure of  $LiNbO_2$  (3) has been recognized as an anti-H-phase type structure (or vice versa). The parent lattice consists of, e.g.,  $Ti_2Al$  and  $NbO_2$ , respectively, and the interstitials are carbon atom and  $Li^+$  ion, respectively. The titanium resp. oxygen atoms occupy the  $4f$  positions (in the  $P6_3/mmc$  space group), which has a free parameter in the  $z$  direction. The small difference for the free parameter  $z$  is due to the preferentially

\* To whom correspondence should be addressed.

ionic bonding in  $\text{LiNbO}_2$ , while in the metallic H-phase a mixed bonding state dominates.

One has to mention furthermore the relatively high stability of these complex carbides considering the competition with the extremely stable binary carbides such as  $\text{TiC}_{1-x}$ ,  $\text{VC}_{1-x}$ , or  $\text{Cr}_3\text{C}_2$ .

Complex carbides and corresponding nitrides, such as  $\text{Ti}_3\text{AlC}$ ,  $\text{Ti}_2\text{AlC}$ , and  $\text{Ti}_2\text{AlN}$ , were recently reported to be of considerable interest because of their outstanding properties as abrasives. It is claimed (4) that these ternary compounds are far superior for glass polishing to the common strong abrasives such as silicon carbide, fused alumina, borides, and carbonitrides of transition elements.

No detailed study of the ternary system Ti-Al-C has been made so far and the same is true for the related systems V-Al-C and Cr-Al-C. These combinations are also attractive insofar as metallic and nonmetallic carbides compete, e.g.,  $\text{TiC}_{1-x}$  and  $\text{Al}_4\text{C}_3$ . As a first approach, isothermal sections at 700, 800, and 1000°C have been investigated. Furthermore, the mutual exchange of the transition element within the H-phase was studied. The results are presented here.

### Sample Preparation

Sample preparation was made on a large scale by sintering as well as by arc melting. The materials used are specified as follows (concentrations in wt%):

Titanium powder (2 N, containing: Ca, 0.4%; Al, 0.35%; Fe, 0.1%; C, 0.015%; Si, 0.003%; Sn, 0.002%; other, 0.003%; from Alpha Div., Ventron Corp.).

Titanium carbide powder (2 N, containing:  $C_{\text{total}}$ , 18.90%;  $C_{\text{free}}$ , 0.25%; O, 0.26%; N, 0.33%; B, Ca, Mg, Ni, Nb, W, 0.02% each; from Alpha Div., Ventron Corp.).

Vanadium powder (2 N, containing: C, 0.09%; Si, 0.08%; Cr, 0.06%; Fe, 0.05%

Al, 0.02%; other, <0.01%; from Alpha Div., Ventron Corp.).

Vanadium carbide powder (2 N, containing:  $C_{\text{total}}$ , 18.90%;  $C_{\text{free}}$ , 0.29%; O, 0.12%; N, 0.1%; W, 0.07%; Cr, 0.05%; Fe, 0.05%; Cu, Si, Zr, 0.02% each; from Alpha Div., Ventron Corp.).

Chromium powder (2 N, containing: Fe, 0.36%; C, 0.02%; Al, 0.02%; S, 0.02%; Si, 0.01%; from Koch-Light Lab. Ltd.).

Aluminium rods (5N5, from Koch-Light Lab. Ltd.).

Aluminium powder (3N8, containing: Fe, <0.1%; Si, 0.05%; other, <0.02%; from Alpha Div., Ventron Corp.).

Graphite rods (reactor grade).

Graphite powder (2N8, containing: Ca, 0.04%; Si, 0.04%; Fe, 0.02%; Al, 0.02%; Si, 0.015%; Ti, 0.01%; from Union Carbide Corp.).

As previously described (5), the preparation of samples was carried out by mixing of the corresponding powders in the proper ratio. As all room temperature operations (weighing, mixing, pressing) were carried out in air, some contamination of the powders by nitrogen or oxygen cannot be ruled out. However, the short exposure times and not-too-small particle sizes (typically 40 to 100  $\mu\text{m}$ ) should have limited this to a minimum. Some samples were prepared starting from master alloys and carbides. After arc melting all samples were sealed in an evacuated quartz tube, annealed at temperatures between 600 and 1200°C (170 to 500 hr), and quenched in water. As some samples showed a tendency to react with the quartz wall, these specimens were placed in a graphite crucible which was then encapsulated in an evacuated quartz tube.

On the basis of an average of 30 samples (5 g each) the isothermal sections have been worked out by means of X-ray analysis. All the binary phases were first corroborated and there was virtually no disagreement with literature data. Similarly the findings concerning the occurrence of the H-phases

and  $Ti_3AlC$  have been confirmed, as can be seen from Tables I-III.

to that of  $TiC_{1-x}$ , however, appears to be due to carbon filling and Ti/Al substitution (see Fig. 1). Similarly for the H-phase, the Ti/Al

**The Ternary System Ti-Al-C**

In Fig. 1, the isothermal section for 1000°C displaying the phase equilibria is presented.  $\beta$ -Titanium has not been retained in the ternary alloy. This is explicable as aluminium and also carbon are  $\alpha$ -stabilizers. Both the complex carbides  $Ti_3AlC$  and  $Ti_2AlC$ , which are the only ternary compounds, determine essentially the phase repartition.  $TiC_{1-x}$ , the most stable phase in addition to graphite, is in equilibrium with  $Al_4C_3$ , Al(l),  $TiAl_3$ ,  $TiAl$ , H-phase, and perovskite phase, but is not in equilibrium with  $Ti_3Al$  at 1000°C. At this temperature, furthermore, the ternary carbides exhibit small homogeneous ranges which unambiguously show up in a variation of the lattice parameters. In particular, the parameter change for the perovskite carbide compared

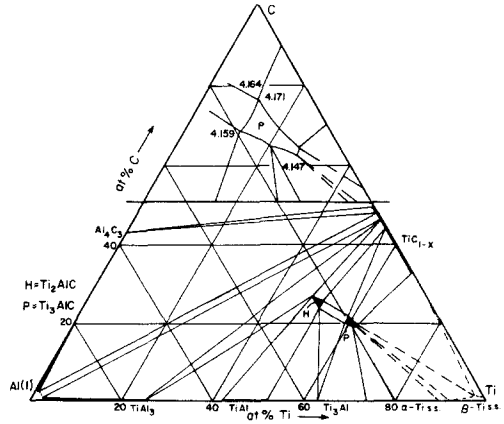


FIG. 1. Isothermal section (annealed at 1000°C) of the Ti-Al-C system; upper part represents the magnified area around the perovskite carbide  $Ti_3AlC$ . From thermochemical data it can be concluded that  $TiC_{1-x}$  and aluminium react, forming  $Al_4C_3$  and  $TiAl_3$  below 800°C.

TABLE I  
PHASES AND LATTICE PARAMETERS IN THE TITANIUM-ALUMINIUM-CARBON SYSTEM

Phases	a (nm)	c (nm)	Literature values (6) (average)	
			a (nm)	c (nm)
<b>Binary<sup>a</sup></b>				
$\alpha$ -Ti (10% at% Al)	0.2934 <sub>8</sub>	0.4691 <sub>5</sub>	0.2934	0.4700
Solid solution (ss)	0.2938 <sub>0</sub> <sup>b</sup>	0.4700 <sub>3</sub> <sup>b</sup>		
$Ti_3Al$	0.5788 <sub>3</sub>	0.463 <sub>7</sub>	0.5765	0.4625
	0.5791 <sub>4</sub> <sup>b</sup>	0.4657 <sub>2</sub> <sup>b</sup>		
$TiAl$ (50 at% Al)	0.3930	0.4074	(49 at% Al) 0.3998	0.4076
$TiAl_3$	0.5440 <sub>4</sub>	0.8585 <sub>3</sub>	0.5446	0.8608
$Al_4C_3$	0.3333 <sub>8</sub> <sup>b</sup>	2.502 <sub>6</sub> <sup>b</sup>	0.3331	2.499
<b>Ternary</b>				
$Ti_2AlC^c$	0.3056 <sub>0</sub> <sup>b</sup>	1.362 <sub>3</sub> <sup>b</sup>	0.304	1.360
$Ti_3AlC^c$	0.4162 <sub>2</sub> <sup>b</sup>		0.415 <sub>6</sub>	

<sup>a</sup> Arc melted, annealed at 700°C, 340 hr.

<sup>b</sup> Arc melted, annealed at 1000°C, 170 hr.

<sup>c</sup> In composition for perovskite.

substitution is more significant than the carbon deficiency. At 700°C no homogeneous range can be detected for the H-phase and very little change of the lattice parameter is observed for the perovskite carbide.

In agreement with the observed lattice parameter change for samples quenched from 1000°C, Ti/Al substitution decreases the lattice parameter while additional carbon content increases the lattice parameter of the perovskite phase. The variation of the H-phase parameters at this temperature has been observed to be between  $a = 0.3045$ ,  $c = 1.363_6$ , and  $a = 0.3065_4$ ,  $c = 1.376_1$  nm. The tie lines characterizing equilibria with the  $\text{TiC}_{1-x}$  carbide were found taking into account the parameter variation from  $0.4333_2$  ( $\text{TiC}_{1-x} + \text{Al}_4\text{C}_3$ ) down to  $0.430_5$  nm ( $\text{TiC}_{1-x} + \text{perovskite} + \alpha\text{-Ti}$ ).

There has been no solubility found for the third component within the binary phases, e.g., carbon in the Ti–Al phases or aluminium in  $\text{TiC}_{1-x}$ . Furthermore, even the solubility of  $\text{TiC}_{1-x}$  in liquid aluminium seems to be small for the temperature region investigated. The ternary carbides form well above 1000°C by peritectic reactions out of  $\text{TiC}_{1-x} + \text{l}$ . In this context it should be mentioned that a more recent development of high-strength aluminium is based on hardening by finely dispersed TiC (7). Investigating Al–TiC alloys Taiichiro (8) has observed at 650°C partial decomposition of TiC, forming  $\text{Al}_4\text{C}_3$  and  $\text{TiAl}_3$  and leading to considerable hardening of aluminium. It should be mentioned furthermore that shock treatment of an Al–TiC composite by explosive techniques yields  $\text{TiAl}_3$  and graphite (H. Nowotny, unpublished).

### The Ternary System V–Al–C

An isothermal section at 1000°C reveals the high stability of the H-phase (Fig. 2). The H-phase coexists with V solid solution,

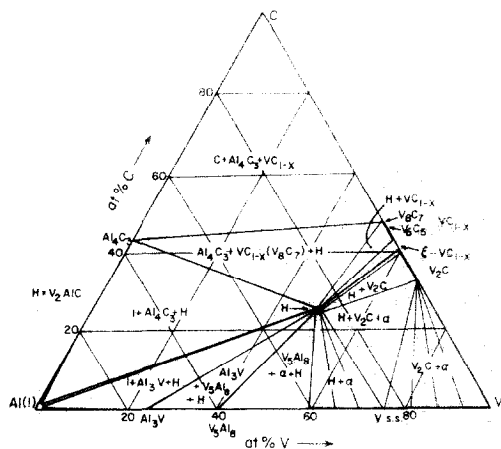


FIG. 2. Isothermal section (annealed at 1000°C) of the V–Al–C system.

Al(l), and all binary compounds, but not with graphite. It is interesting to mention the coexistence of the H-phase with aluminium. Virtually no homogeneity region was found for the H-phase and the same is true for the participating binary phases with respect to the third component. In particular no influence of aluminium on the vanadium carbides can be detected so far. For the 1000°C anneal the monocarbide showed up in the disordered state  $\text{VC}_{1-x}$  and in the ordered state  $\text{V}_8\text{C}_7$  as well. Similarly the ordered subcarbide phase  $\text{V}_2\text{C}$  having  $\zeta\text{-Fe}_2\text{N}$ -type structure has been found unchanged in the ternary system. The equilibrium concentration of the V solid solution with H-phase +  $\text{V}_2\text{C}$  can be determined from lattice parameter measurements to be about 23 at% Al. The newly obtained parameters for the occurring phases are listed with some literature data in Table II.

### The Ternary System Cr–Al–C

The equilibria are shown in Figs. 3a and b for isothermal sections at 800 and 1000°C. The major feature again is the existence of only one ternary carbide which is the H-phase. At 800°C, in the presence of graphite,

TABLE II

PHASES AND LATTICE PARAMETERS IN THE VANADIUM-ALUMINIUM-CARBON SYSTEM

Phases	<i>a</i> (nm)	<i>b</i> (nm)	<i>c</i> (nm)	Literature data ( $\delta$ )	
				<i>a</i> (nm)	<i>c</i> (nm)
Binary					
V ss (50 at% Al) arc melted, annealed at 1000°C, 170 hr	0.30708			0.3075 <sub>5</sub> 0.3068	
Two-phase V <sub>5</sub> Al <sub>8</sub> (59.5 at% Al)	0.9218 <sub>6</sub>			0.9205 (Two-phase, at 50 at% Al)	
VAl <sub>3</sub> , arc melted, annealed at 700°C, 320 hr	0.533 <sub>5</sub>		0.8288	0.5345	0.8322
V <sub>2</sub> C, arc melted, annealed at 1000°C, 170 hr	0.457 <sub>7</sub> -0.4602	0.5742-0.575 <sub>1</sub>	0.5037-0.5025 <sub>5</sub> <sup>a</sup>		
$\zeta$ -VC	0.4127			0.4129	
V <sub>8</sub> C <sub>7</sub>	0.8038-0.8313 <sub>3</sub>			0.8333	
VC <sub>1-x</sub>	0.4154-0.4158 <sub>4</sub>			0.4150 <sub>6</sub> -0.4162	
Ternary					
V <sub>2</sub> AlC	0.2911 <sub>6</sub>		1.3140	0.291 <sub>3</sub>	0.131 <sub>4</sub>

<sup>a</sup> V-rich to C-rich.

the ternary carbide is more stable than the binary carbides Cr<sub>3</sub>C<sub>2</sub> and Al<sub>4</sub>C<sub>3</sub>. At the higher temperature, the H-phase was found to be less stable as compared to Cr<sub>3</sub>C<sub>2</sub> and Al<sub>4</sub>C<sub>3</sub>; therefore, the reaction H + graphite = Cr<sub>3</sub>C<sub>2</sub> + Al<sub>4</sub>C<sub>3</sub> near 1000°C has to be assumed. No significant solubility region has been detected for the H-phase and no solubility has been found within the binary compounds for the third component either. As shown in Table III, the observed lattice parameters of the various participating phases are consistent with literature data for the binary systems.

For both the temperature sections, there is no coexistence between H and Cr<sub>23</sub>C<sub>6</sub> on the one side and H and the Al-rich phases,  $\theta$ ,  $\eta$ , and  $\varepsilon$ , on the other, thus differing considerably from the former system.

### The Partial Systems Ti<sub>2</sub>AlC-V<sub>2</sub>AlC-Cr<sub>2</sub>AlC

Mutual substitution of the transition element in H-phases has been shown to occur for (Zr, Nb)<sub>2</sub>AlC (9) or for (Ti, V)<sub>2</sub>SC (10) but no systematic approach has been made so far. Therefore, a study was carried out for the neighboring elements, Ti, V, and Cr.

First, the corresponding H-phases were prepared and checked for homogeneity. A series of powder mixtures in proportions of 25, 50, and 75 mole% was then heated up for reaction at 1000°C for 170 hr in evacuated, sealed quartz tubes.

X-Ray powder diagrams of the obtained products revealed already a strong tendency for forming solid solutions, but the equilibrium state had not always been reached after this reaction time.

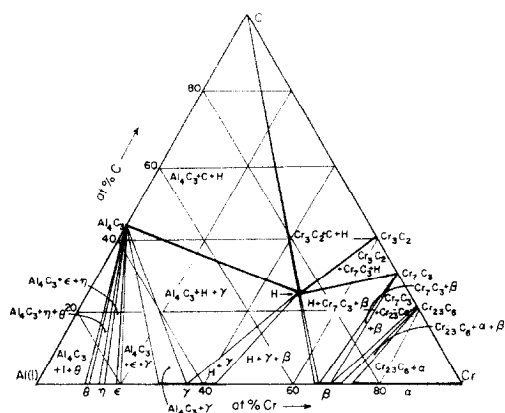


FIG. 3a. Isothermal section (annealed at 800°C) of the Cr-Al-C system.

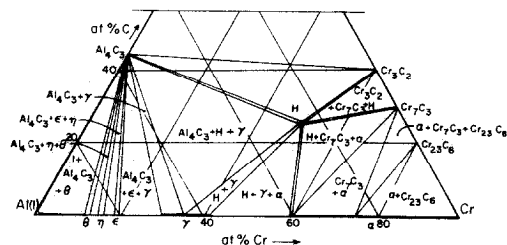


FIG. 3b. Isothermal section (annealed at 1000°C) of the Cr-Al-C system.

### $Ti_2AlC-V_2AlC$

As can be seen from Table IV, there is a complete solid solution observed between these H-phases. The cell parameters change almost linearly, although the  $a$  parameter undergoes a slightly negative deviation (compression).

### $V_2AlC-Cr_2AlC$

The results for  $V_2AlC-Cr_2AlC$  differ somewhat, insofar as the reaction after 170 hr was obviously incomplete. The powder diagrams for 25 and 50 mol%  $Cr_2AlC$  still reveal the existence of two H-phases, the lattice parameters of one H-phase still corresponding to those of  $V_2AlC$ . The nonequilibrium state furthermore is clearly indicated by the diffuse lines of the other H-phase in the powder pattern. Prolonged reaction time leads again to complete formation of a continuous solid solution (V, Cr) $_2AlC$  (see Table IV).

### $Ti_2AlC-Cr_2AlC$

No continuous transition of these H-phases has been observed even after a very

TABLE III  
PHASES AND LATTICE PARAMETERS IN THE CHROMIUM-ALUMINIUM-CARBON SYSTEM

Phases	$a$ (nm)	$b$ (nm)	$c$ (nm)	Literature data ( $\delta$ )		
				$a$ (nm)	$b$ (nm)	$c$ (nm)
<b>Binary</b>						
Cr ss						
(25 at% Al)	0.2939			0.294 <sub>5</sub>		
				(24 at% Al)		
$Cr_2Al$						
(30 at% Al)	0.2974 <sub>5</sub>		0.8697	0.2990		0.8659
						(29.3 at% Al)
(40 at% Al)	0.2996 <sub>5</sub>		0.8655	0.3001		0.8637
						(34 at% Al)
$Cr_{23}C_6$	1.0655			1.0659		
$Cr_7C_3$	1.4031		0.4528	1.401		0.4532
$Cr_3C_2$	1.1466	0.5524	0.2828	1.148	0.553	0.2827
<b>Ternary</b>						
$Cr_2AlC$	0.286 <sub>6</sub>		1.282 <sub>5</sub>	0.286 <sub>0</sub>		1.28 <sub>2</sub>

TABLE IV  
 LATTICE PARAMETERS OF H-PHASE SOLID SOLUTIONS (ANNEALED AT 1000°C)

Partial system	$a$ (nm)	$c$ (nm)	Notes
<b>Ti<sub>2</sub>AlC–V<sub>2</sub>AlC</b>			
Ti <sub>2</sub> AlC	0.3052	1.364	Starting material
Ti <sub>1.5</sub> V <sub>0.5</sub> AlC	0.3011	1.351 <sub>0</sub>	Anneal, 1 week
Ti V AlC	0.2975	1.339 <sub>3</sub>	Anneal, 1 week
Ti <sub>0.5</sub> V <sub>1.5</sub> AlC	0.2927	1.327 <sub>7</sub>	Anneal, 1 week
V <sub>2</sub> AlC	0.2909	1.312 <sub>7</sub>	Starting material
<b>V<sub>2</sub>AlC–Cr<sub>2</sub>AlC</b>			
V <sub>1.5</sub> Cr <sub>0.5</sub> AlC	0.2903	1.305 <sub>4</sub>	Anneal, 2 weeks
V CrAlC	0.2893	1.297 <sub>0</sub>	Anneal, 5 weeks
V <sub>0.5</sub> Cr <sub>1.5</sub> AlC	0.2873	1.292 <sub>8</sub>	Anneal, 2 weeks
Cr <sub>2</sub> AlC	0.2854	1.282	Starting material
<b>Cr<sub>2</sub>AlC–Ti<sub>2</sub>AlC</b>			
Cr <sub>1.5</sub> Ti <sub>0.5</sub> AlC	0.2901	1.310 <sub>5</sub>	Anneal, 3 weeks
CrTiAlC	—	—	No H-phase
Cr <sub>0.5</sub> Ti <sub>1.5</sub> AlC	0.3041	1.3593	Minor amount of H-phase

long reaction time. Only a limited mutual solubility, which goes up on the chromium side to 25 mole% Ti<sub>2</sub>AlC, and on the titanium side to about 6 mol% Cr<sub>2</sub>AlC, has been detected (see Table IV). There is, however, no simple miscibility gap (pseudo-binary section) between these H-phase solid solutions, because in addition to TiC<sub>1-x</sub> other nonidentified phases occur. This may be due to the relatively high solubility of Cr<sub>3</sub>C<sub>2</sub> in TiC<sub>1-x</sub>, competing with the H-phase stability. Furthermore, the size difference of the metal atoms is largest for this partial system.

From this point of view, the substitution tendency is expected to be strongest for vanadium and chromium. On the other hand, as can be seen from the carbide behavior of TiC<sub>1-x</sub> and VC<sub>1-x</sub>, the easy formation of (Ti, V)C<sub>1-x</sub> solid solutions certainly is a hint of the fast reaction of the corresponding H-phases.

### Acknowledgment

This work has been supported by the National Science Foundation through Grant DMR77-20504 to the

University of Connecticut. The authors gratefully acknowledge the award.

### References

1. H. NOWOTNY, *Angew. Chem.* **84**, 973 (1972).
2. H. NOWOTNY, H. BOLLER, AND O. BECKMANN, *J. Solid State Chem.* **2**, 462 (1970).
3. G. MEYER AND R. HOPPE, *J. Less Common Metals* **46**, 55 (1976).
4. V. I. IVCHENKO AND T. YA. KOSOLAPOVA, *Porosh. Met.* **150**, 1 (1975); V. I. IVCHENKO, M. I. LESNAYA, V. F. NEMCHENKO, AND T. YA. KOSOLAPOVA, *Porosh. Met.* **161**, 45 (1976); V. I. IVCHENKO AND T. YA. KOSOLAPOVA, *Porosh. Met.* **164**, 56 (1976); see also A. HARA AND S. YAZU, *Japan Kokai*, 7478712, 7478713 (1974).
5. W. JEITSCHKO, Thesis, University of Vienna (1964).
6. W. B. PEARSON, "A Handbook of Lattice Spacings and Structures of Metals and Alloys," Vol. 2, Pergamon, Oxford (1967).
7. G. JANGG, F. KUTNER, AND G. KORB, *Aluminium* **51**, 641 (1975).
8. M. TAIICHIRO, *Keikinzo* **20**, 15 (1970).
9. E. REIFFENSTEIN, H. NOWOTNY, AND F. BENESOVSKY, *Monatsh. Chem.* **97**, 1427 (1966).
10. O. BECKMANN, Thesis, University of Vienna (1970).